

AD-A160 770

PRELIMINARY STUDY OF HOLOGRAPHIC INTERFEROMETRY APPLIED  
TO CARBON FIBRE SPECIMENS(U) AERONAUTICAL RESEARCH LABS  
MELBOURNE (AUSTRALIA) B L LAWRIE AUG 85

1/1

UNCLASSIFIED

ARL/STRUC-TN-419


F/G 11/5

NL

END

FILED

DTIC

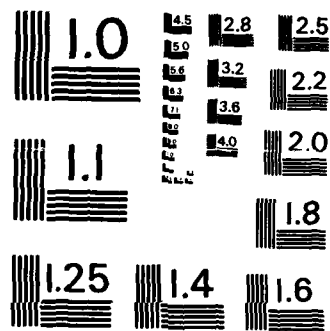

MICROCOPY RESOLUTION TEST CHART  
NATIONAL BUREAU OF STANDARDS-1963-A

UNCLASSIFIED

12

ARL-STRUC-TM-419

AR-004-038



## DEPARTMENT OF DEFENCE

DEFENCE SCIENCE AND TECHNOLOGY ORGANISATION

AERONAUTICAL RESEARCH LABORATORIES

MELBOURNE, VICTORIA

AD-A160 770

Structures Technical Memorandum 419

### PRELIMINARY STUDY OF HOLOGRAPHIC INTERFEROMETRY APPLIED TO CARBON FIBRE SPECIMENS

by

Brian L. LAWRIE

Approved for Public Release

THE UNITED STATES NATIONAL  
TECHNICAL INFORMATION SERVICE  
IS AUTHORIZED TO  
REPRODUCE AND SELL THIS REPORT

DTIC  
ELECTE  
OCT 31 1985

E

(C) COMMONWEALTH OF AUSTRALIA 1985

AUGUST 1985

UNCLASSIFIED  
85 10 31 070

NTIC FILE COPY

## Department of Defence

## DOCUMENT CONTROL DATA

1. a. AR No AR-004-038	1. b. Establishment No ARL-STRUC-TM-419	2. Document Date AUGUST 1985	3. Task No DST 83/006
4. Title  PRELIMINARY STUDY OF HOLOGRAPHIC INTERFEROMETRY APPLIED TO CARBON FIBRE SPECIMENS		5. Security a. document UNCLASSIFIED	6. No Pages 7
		b. title U	c. abstract U
8. Author(s)  BRIAN L. LAWRIE		9. Downgrading Instructions	
10. Corporate Author and Address  Aeronautical Research Laboratories P.O. Box 4331, Melbourne, Vic 3000		11. Authority (as appropriate) a. Sponsor b. Security c. Downgrading d. Approval	
12. Secondary Distribution (of this document)  Approved for Public Release			
Overseas enquirers outside stated limitations should be referred through ASDIS, Defence Information Services Branch, Department of Defence, Campbell Park, CANBERRA ACT 2601			
13. a. This document may be ANNOUNCED in catalogues and awareness services available to ...  No Limitations			
13. b. Citation for other purposes (ie casual announcement) may be (select) unrestricted (or) as for 13 a.			
14. Descriptors  Holographic interferometry, Graphite-epoxy composites		15. COSATI Group  11040 20050	
16. Abstract  Holographic interferometry has been used to examine two carbon fibre compression specimens with known defects. Photographs of the reconstructed images of the specimens clearly indicate the location of the defects.			

This page is to be used to record information which is required by the Establishment for its own use but which will not be added to the DISTIS data base unless specifically requested.

16. Abstract (Contd)		
17. Imprint  Aeronautical Research Laboratories, Melbourne.		
18. Document Series and Number  Structures Technical Memorandum 419	19. Cost Code  24 6930	20. Type of Report and Period Covered
21. Computer Programs Used		
22. Establishment File Ref(s)		

DEPARTMENT OF DEFENCE  
DEFENCE SCIENCE AND TECHNOLOGY ORGANISATION  
AERONAUTICAL RESEARCH LABORATORIES

AR-004-038

Structures Technical Memorandum 419

PRELIMINARY STUDY OF HOLOGRAPHIC INTERFEROMETRY  
APPLIED TO CARBON FIBRE SPECIMENS

by

Brian L. LAWRIE

SUMMARY

Holographic interferometry has been used to examine two carbon fibre compression specimens with known defects. Photographs of the reconstructed images of the specimens clearly indicate the location of the defects.



(C) COMMONWEALTH OF AUSTRALIA 1985

---

POSTAL ADDRESS: Director, Aeronautical Research Laboratories,  
P.O. Box 4331, Melbourne, Victoria, 3001, Australia.

## CONTENTS

Page No.

1.	INTRODUCTION.....	1
2.	THEORY.....	1
2.1	Holography.....	1
2.2	Holographic Interferometry.....	1
3.	EXPERIMENTAL.....	2
3.1	Introduction.....	2
3.2	Set Up.....	2
3.3	Specimens.....	2
3.4	Recording and Reconstruction of Holograms...	3
4.	RESULTS.....	3
5.	DISCUSSION.....	3
6.	CONCLUSION.....	4

ACKNOWLEDGEMENT

FIGURES

DISTRIBUTION LIST

DOCUMENT CONTROL DATA

Accession For	
NTIS GRA&I	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By _____	
Distribution/ _____	
Availability Codes	
Avail and/or _____	
Dist _____	Special _____
A-1	



## 1. INTRODUCTION

The increased use of carbon fibre materials in modern aircraft design has led to the requirement for a non destructive technique to quickly examine large areas of carbon fibre surfaces. The ability of holographic interferometry to detect very small deformations over large areas has led to research in holography as a technique of inspection. This report gives details of a preliminary study of the use of holographic interferometry to locate impact damage and simulated delamination in 20 ply compression F/A-18 type, graphite epoxy specimens.

## 2. THEORY

### 2.1 Holography

Holography is the science of recording an entire optical wavefront, both phase and amplitude information, on a suitable recording material. Such a record is called a hologram.

To construct a hologram, a beam of laser light (which is both monochromatic and coherent) is split into two beams as shown schematically in Fig. 1. Each beam passes through a spatial filter, which consists of a microscope objective with a pinhole ( $10\mu$ ) at its focus. This spatially filters the light and converts the plane wave beam into a diverging spherical wave. One beam illuminates the object which is to be holographed, the other, acting as a reference beam illuminates a photographic plate which is to record the hologram. The light rays reflected and scattered from the object interfere with the reference rays. Because the light of both beams has temporal and spatial coherence, constructive and destructive interference will occur. The photographic plate, located in the region of interference, records phase and amplitude information of the combining rays. After processing, the plate is illuminated in light of similar wavelength to the recording light. The silver particles in the emulsion diffract the light rays and 'replay' an exact duplicate of the original wavefront coming from the object. The wavefront reconstructs an image which is identical in appearance to the original object.

### 2.2 Holographic Interferometry

Holographic interferometry consists of recording two successive holographic exposures of an object in two different positions (eg. before and after the application of stress). The two exposures are recorded on the same plate. The object is stressed between exposures and upon reconstruction of the double exposure hologram, combined images of the object will be formed. Since both reconstructed images are formed in coherent light and exist at approximately the same location in space, they will interfere with each other and produce a set of bright and dark interference fringes in the reconstructed hologram.



Each fringe represents a surface displacement of approximately half the wavelength of the laser light. The fringes could represent shifts in all three planes - X, Y and Z. However in these experiments most of the displacement would be changes in distance between the surface of the specimen and the photographic plate (Z axis).

### 3. EXPERIMENTAL

#### 3.1 Introduction

The recording of holograms requires extreme stability of all optical components, as minute vibrations will prevent the recording of the object's wavefront. To ensure adequate stability it is necessary to have a stable optical table with good vibration isolation from the floor and adequate damping characteristics.

#### 3.2 Set Up

The optics table consisted of a terrazzo slab supported by a welded angle iron framework. Rubber blocks separated the slab and the framework. The framework was isolated from the floor by partly inflated rubber tubes, which rested on felt pads. An interferometer assembled on the table indicated that some vibrations were reaching the table top, but were not of sufficient intensity to prevent double exposure recordings.

The light source for the experiments was a continuous wave, 3 watt multi-line argon-ion laser. In this case the distance between fringes is 257 nanometers or 0.25 of a micron. Therefore a count of 4 fringes is a total surface shift between the two points of 1 micron. A Fabry-Perot etalon was fitted into the rear cavity enabling it to be tuned to a single line longitudinal mode of operation at approximately 514 nm, thus ensuring a long coherence length. The laser was on a different table to the optical components to prevent vibrations from its water cooling system entering the optics table.

To construct the holograms the optical components were arranged in the manner described in section 2.1 and shown schematically in Fig. 1. Fig. 2 shows the actual experimental arrangement, with the exception of light stops and screens which were removed to enable all of the optical components to be seen. The components were positioned so that the reference beam and object beam pathlengths were approximately the same. Power output from the laser was set at 140 milliwatts. The light intensity ratio of the reference beam and reflected object beam upon the recording plate was set at approximately two to one. This was achieved by adjusting the variable beamsplitter and monitoring shadow intensities on the plate area.

#### 3.3 Specimens

Two carbon fibre specimens, both with some form of defect, were examined. The first of these was a 20 ply coupon compression F/A-18 type graphite/epoxy specimen having two 15 mm diameter, 0.05 mm thick Teflon discs located on top of each other between the second and third layers. The lay up of this specimen simulated a delamination defect.

The second specimen was also a 20 ply coupon compression F/A-18 type graphite/epoxy coupon. However the defect in this case resulted from impact damage. This damage was caused by dropping an impactor onto the laminate while it was supported by honeycomb core material. The impactor, of total mass 1.37 kg, had a head of 25 mm diameter and was dropped from 500 mm above the specimen.

#### 3.4 Recording and Reconstruction of Holograms

Prior to recording the hologram the specimen was heated to about 50°C with a hot air blower. A "G" clamp held the specimens in place on the table. During cooling two exposures of 1 second each were taken with a time interval of 1 minute between exposures. The surface movement which took place during this interval is represented by the fringes in the reconstructed hologram. Exposure was controlled by a camera shutter mounted in the beam path at the laser's aperture. The plates were developed in Kodak D19 developer for 4 minutes at 20°C, then completely bleached out to form a phase hologram.

The images were reconstructed by placing the plates in a diverging beam of light similar to the original reference beam used in the construction of the holograms. The images were photographed with a 35 mm camera using a standard 50 mm lens fitted with a 10 mm extension ring. Film used was Kodak type Technical Pan 2415. Image speckle was eliminated by setting the aperture of the camera at f5.6.

#### **4. RESULTS**

Reconstructed images of the front surface of the simulated delamination specimen, and both surfaces of the impact damaged specimen are shown in Figures 3-5. Ultrasonic C-scans are shown in Figures 6 and 7 for comparison with the reconstructed images.

#### **5. DISCUSSION**

The relative surface movements during stressing, as shown in the reconstructed images, clearly indicates large surface shifts in the region of the defects. These surface shifts were revealed as a series of circular contours, which enables a measurement to be made of the defect's position. At this stage no quantitative fringe interpretation has been attempted. However some qualitative information can be obtained.

In Figure 5, showing the rear surface of the impact damaged specimen, the fringes towards the lower right of the damaged region display discontinuities. The discontinuities of the fringes form lines which are approximately parallel to the direction of fibres in one of the layers. This could indicate fibre damage in a particular layer. The general similarity between the delaminated specimen and the impact damaged specimen may indicate that delamination has occurred during impact damage. A comparison of the size of the area covered by the fringes on the front and back surfaces of the impact damage specimen reveals that the area of damage tends to expand through the depth of the specimen.

## 6. CONCLUSION

Two carbon fibre coupon, compression F/A-18 type specimens, with known defects representing delamination and impact damage, have been examined using holographic interferometry. Double exposure holograms were taken during contraction of the specimen, after heating to 50°C. The locations of the defects were clearly visible in the reconstructed images.

## ACKNOWLEDGEMENT

I acknowledge Bill Broughton of Materials Division, Aeronautical Research Laboratories for his help and advice concerning the carbon fibre specimens, and Thomas Preuss for supplying the ultrasonic details.

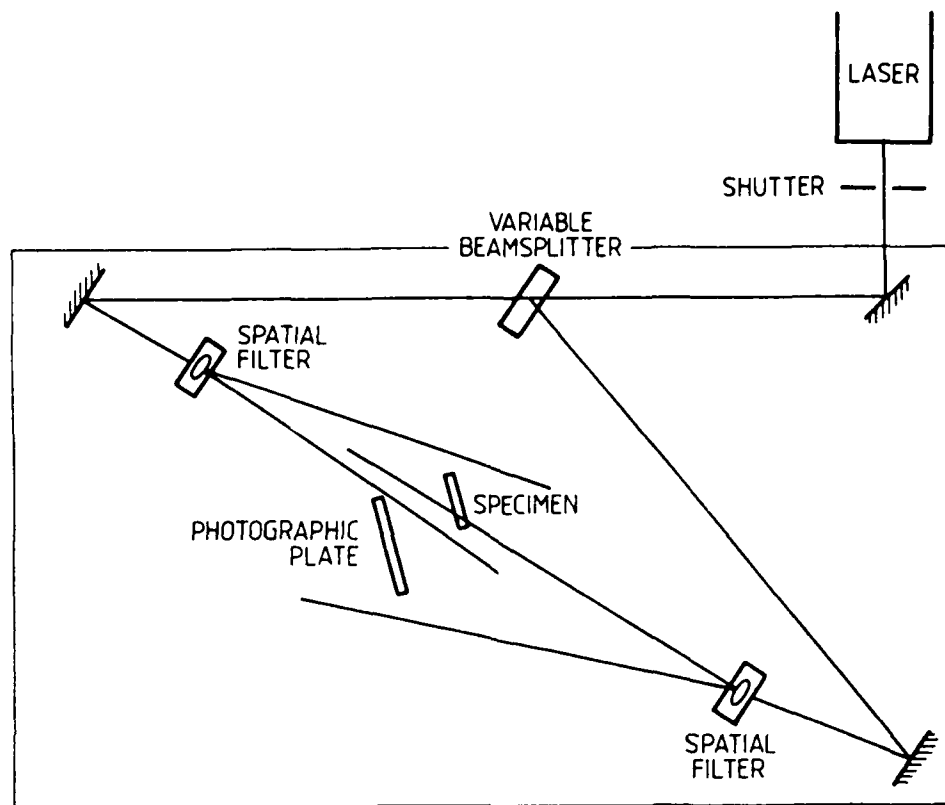


FIGURE 1: DIAGRAM OF OPTICAL COMPONENTS ON THE TABLETOP FOR THE CONSTRUCTION OF THE HOLOGRAMS

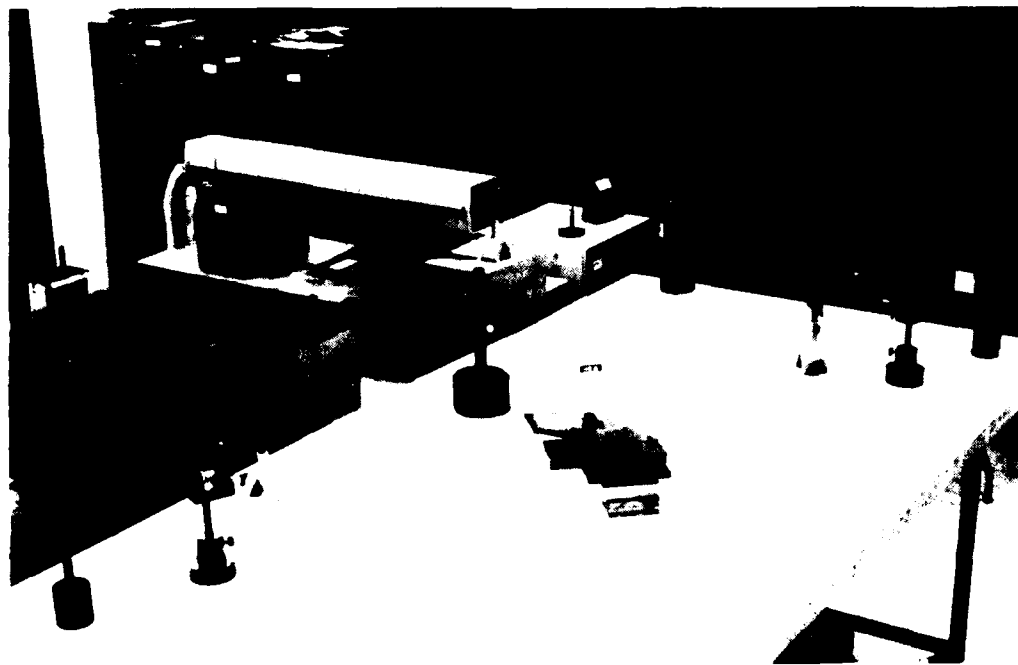


FIGURE 2: OPTICAL ARRANGEMENT FOR THE CONSTRUCTION OF THE HOLOGRAMS



FIGURE 3: FRONT SURFACE OF SIMULATED DELAMINATION SPECIMEN

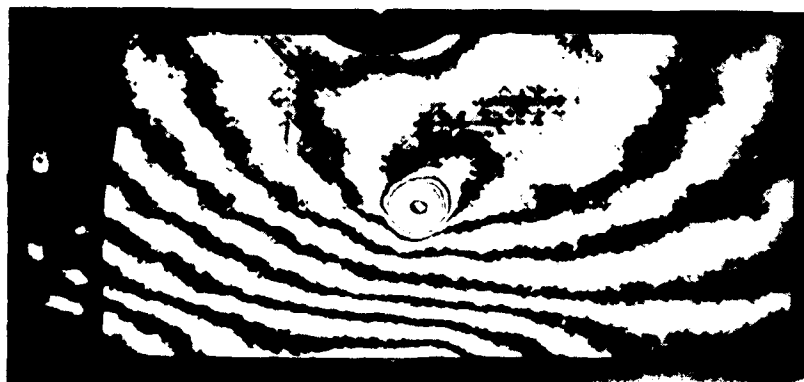


FIGURE 4: FRONT SURFACE OF IMPACT DAMAGE SPECIMEN

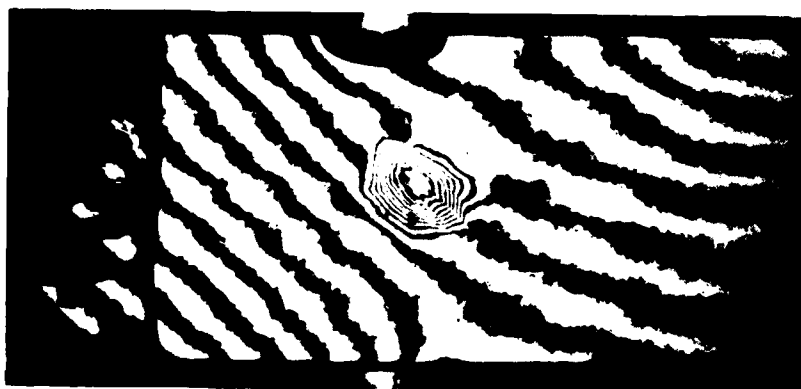


FIGURE 5: REAR SURFACE OF IMPACT DAMAGE SPECIMEN

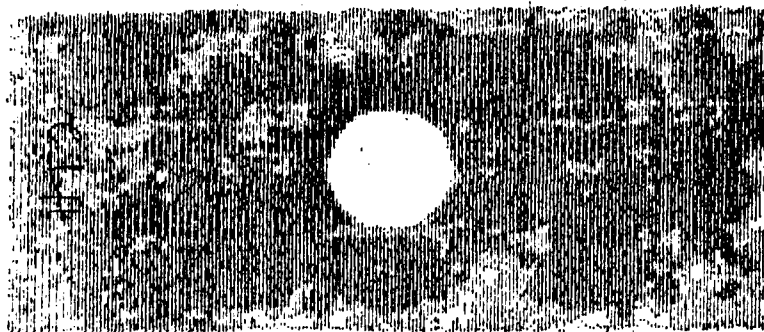


FIGURE 6: ULTRASONIC C-SCAN OF ARTIFICIALLY DELAMINATED SPECIMEN

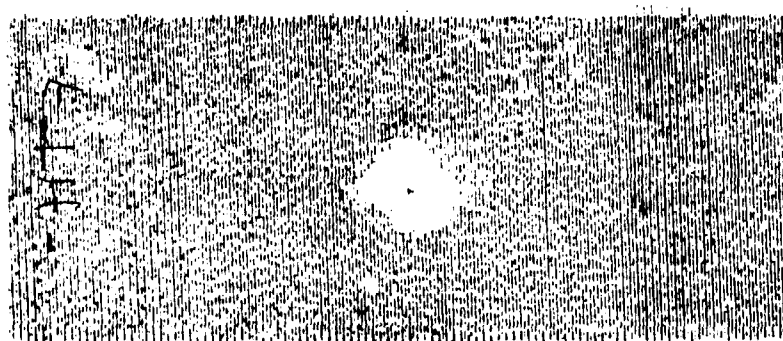


FIGURE 7: ULTRASONIC C-SCAN OF IMPACT DAMAGED SPECIMEN

## DISTRIBUTION LIST

### AUSTRALIA

#### DEPARTMENT OF DEFENCE

##### Defence Central

Chief Defence Scientist )  
Deputy Chief Defence Scientist )  
Superintendent, Science and Program Administration ) (1 copy)  
Controller, External Relations, Projects & Analytical Studies )  
Defence Science Adviser (UK) (Doc Data sheet only)  
Counsellor, Defence Science (USA) (Doc Data sheet only)  
Defence Central Library  
Document Exchange Centre, DISB (18 copies)  
Joint Intelligence Organisation  
Librarian H Block, Victoria Barracks, Melbourne

##### Aeronautical Research Laboratories

Director  
Library  
Superintendent - Aerodynamics  
Superintendent - Aero Propulsion  
Superintendent - Aircraft Materials  
Divisional File - Structures  
Superintendent - Systems  
E. Moody  
A.A. Baker  
W. Broughton  
J.G. Sparrow  
S.J. Rumble  
K. Watters  
A. Farrell  
Author: B.L. Lawrie

##### Army Office

Engineering Development Establishment, Mr S.C. Austin

##### Air Force Office

C O, Central Photographic Establishment, Laverton

### UNIVERSITIES AND COLLEGES

RMIT Mr P. Francis, Department of Physics

SPARES (15 copies)  
TOTAL (55 copies)

**END**

**FILMED**

**12-85**

**DTIC**